

Application of U-FAST Technology in Sintering of Titanium Biomaterials

Katarzyna Jach^{1*}, Paweł Figiel² and Anna Biedunkiewicz²

¹Geni Core Sp. z o.o., Poland

²Institute of Materials Science and Engineering, Poland

*Corresponding author: Katarzyna Jach, GeniCore Sp z oo, Wolczyńska 133, 01-919 Warsaw, Poland



ARTICLE INFO

Received: 📅 November 26, 2019

Published: 📅 December 02, 2019

ABSTRACT

Citation: Katarzyna Jach, Paweł Figiel, Anna Biedunkiewicz. Application of U-FAST Technology in Sintering of Titanium Biomaterials. Biomed J Sci & Tech Res 23(3)-2019. BJSTR. MS.ID.003906.

Short Communication

The titanium has been a part of the group of materials used in areas where excellent corrosion resistance and high strength are required. Due to its outstanding properties it is used in medicine, mainly thanks to biocompatibility and corrosion resistance in the environment of body fluids. It is used to make implants, stents and prostheses. Nevertheless, the titanium main disadvantage, apart from high manufacturing costs, is its relatively low wear resistance. The Titanium Metal Matrix Composites (TMMCs) are increasingly used to eliminate this disadvantage. Hard ceramic reinforcement phases in the form of fiber or powders, e.g. SiC, TiC, Al₂O₃, TiB₂, are often added to the metallic titanium matrix for this purpose [1-7]. The preliminary studies of titanium composites reinforced with nanocrystalline powders from (Ti,Mo)C/C system are presented by this paper.

The powders were sintered using an SPS-type furnace (U-FAST, GeniCore, Poland). Recent years have showed significant developments in the methods of sintering by activated electric field. These methods allow to perform the sintering process in a very short period of time from a few to several minutes, thus reducing the unfavorable grain growth in the consolidated material. In these techniques the sintering process is performed at a uniaxial pressure. U-FAST (Upgraded Field Assisted Sintering Technology) having a characteristic method of powder heating. The innovative solutions open the perspective for sintering of the new materials and has unique characteristics. Pulse power modular supplies offer the shortest impulse duration, less than 1ms. Together with

the higher power supply voltage (14 V), they make this technology effective, energy-saving and dedicated to the consolidation of nanocrystalline materials [8,9].

Experimental

As starting matrix material, the one type of cp-Ti powder (grade 1), with a spherical shape and its average particle size around 100µm from SLM Solutions GmbH, was employed. As a reinforcements two type of nanoparticles were used: (Ti,Mo)C with an average crystallite size of 25nm and (Ti,Mo)C/C carbides embedded in carbon network with an average crystallite size of 12nm and ca 40wt.% elemental carbon. Before the sintering titanium with reinforcing carbides phase was milled during 12h, in order to obtain a uniform mixing of powders. Sintering processes were conducted in high vacuum (10-5mbar). Powder mixtures were placed into cylindrical graphite die with inner diameter of 20mm. The pulse sequence was set to 1:1 (tON:tOFF). The temperature was monitored by an axial and a side optical pyrometer. Samples were heated to the desired temperatures with the ramp of 400°C/min. Sintering temperature was 1050°C and 1150°C with 2min and 24min of dwell time, respectively. In all cases, the U-FAST was performer under uniaxial mechanical pressure of 50 MPa, applied during the whole sintering process, including heating ramps and cooling. The density was determined by hydrostatic method after ultrasonic cleaning and vacuum drying. The microhardness was measured by Vickers method under load 100g. Potentiodynamic polarization measurements were carried out on the Atlas-Sollich

9833 potentiostat in a three-electrode system. The parameters of the test were as follows: a scan rate of 0.01V/s at a potential initiated at -1.2V to +2.0V. The calomel (reference) and graphite (auxiliary) electrodes were used. The analysis of the results has been carried out by means of the AtlasLab software. Pure titanium (cp-Ti) and Ti-6Al-4V alloy were used as reference samples.

Results

The sintering processes of titanium materials with the addition of titanium strengthening phases (Ti,Mo)C and (Ti,Mo)C/C were carried out. The materials were sintered at 1050°C, which allowed

to obtain a density of samples corresponding to theoretical values. In the case of addition 20% (Ti,Mo)C/C the minimum temperature to achieve total compaction was 1150°C with dwell time 24min. The density after sintering at 1050°C was 3.86g/cm³, thus not been studied. The obtained values are summarized in (Tables 1 & 2). Vickers hardness measurements made at different locations on the surface of each samples are summarized in (Figure 1). The samples were polished to a mirror finish before the hardness measurement. The measured hardness was observed to be near uniform throughout each sintered sample, indicating uniform densification.

Table 1: Density of titanium-based materials.

Material	cp-Ti	Ti-6Al-4V	Ti+10wt.% (Ti,Mo)C	Ti+20wt.% (Ti,Mo)C	Ti+10 wt.% (Ti,Mo)C/C	Ti+20 wt.% (Ti,Mo)C/C
Density, g/cm ³	4.5	4.46	4.66	4.7	4.65	4.72

Table 2: Corrosion parameters of sintered materials- Ringer solution.

Material	cp-Ti	Ti-6Al-4V	Ti+20wt.% (Ti,Mo)C	Ti+10wt.% (Ti,Mo)C/C	Ti+20wt% (Ti,Mo)C/C
Corrosion potential E_{corr} , V	-0.328	-0.392	-0.427	-0.643	-0.498
Corrosive current I_{corr} , A/cm ²	$2.1 \cdot 10^{-6}$	$2.3 \cdot 10^{-6}$	$6.28 \cdot 10^{-6}$	$8.26 \cdot 10^{-6}$	$10.37 \cdot 10^{-6}$

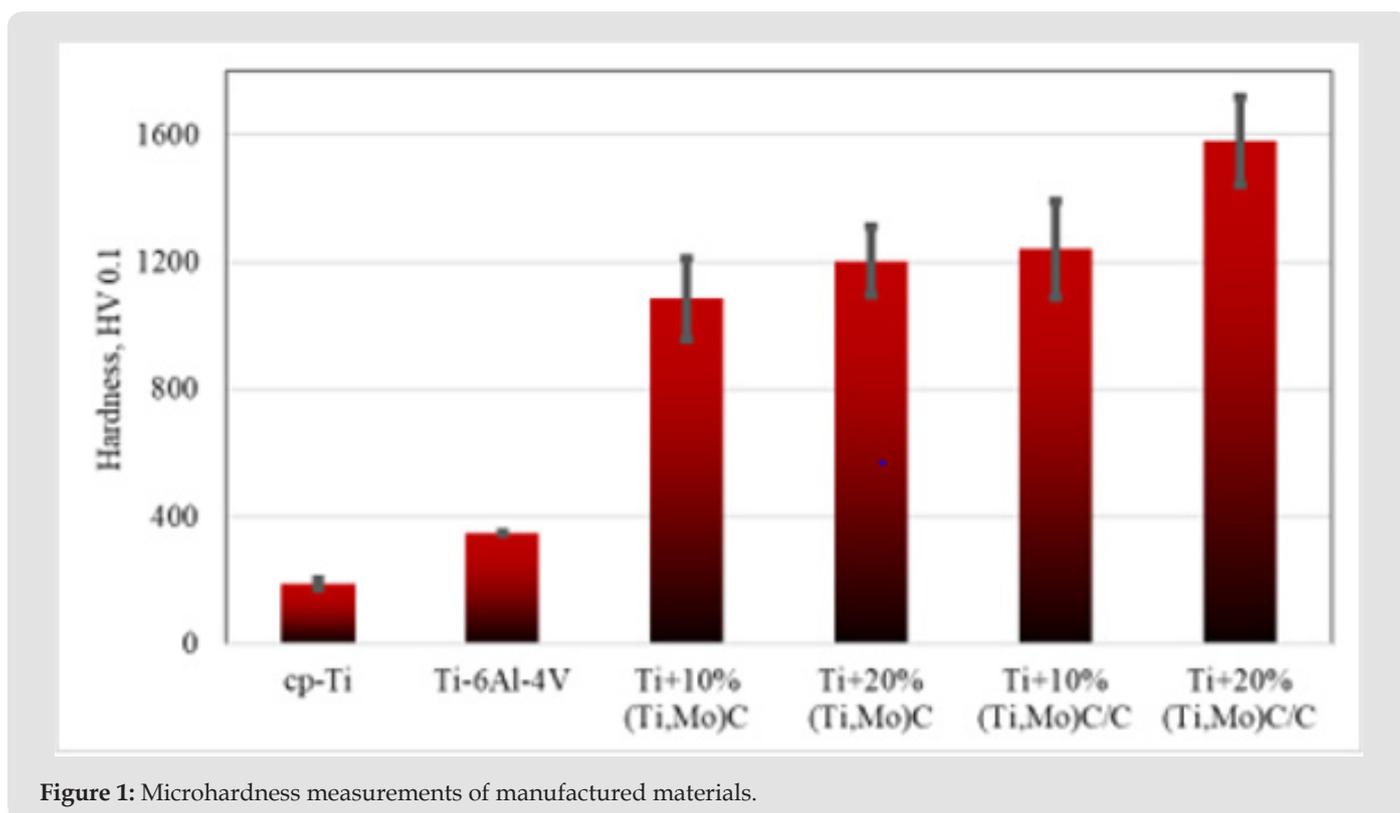


Figure 1: Microhardness measurements of manufactured materials.

Based on images from an Optical Microscope (OM), the microstructure of the tested materials was determined. Pictures are shown in (Figure 2). In the case of pure titanium, a typical needle (dendritic) structure is visible (Figure 2a). For the Ti-6Al-4V alloy (Figure 2b), the bi-modal microstructure of titanium α and β is observe. The lighter fields are the α phase, while the darker fields are the Widmanstätten phase. Figures 2 c-f show the microstructure

of composites with a strengthening phase. The greater addition of this phase has a positive effect on the homogeneity of the material, which is confirmed by measurements of both density and hardness. Smaller amounts of matrix are visible in the case of (Ti,Mo)C/C type of carbides, due to the reaction of free carbon with the titanium matrix. This is especially visible in the case of 20% (Ti,Mo)C/C.

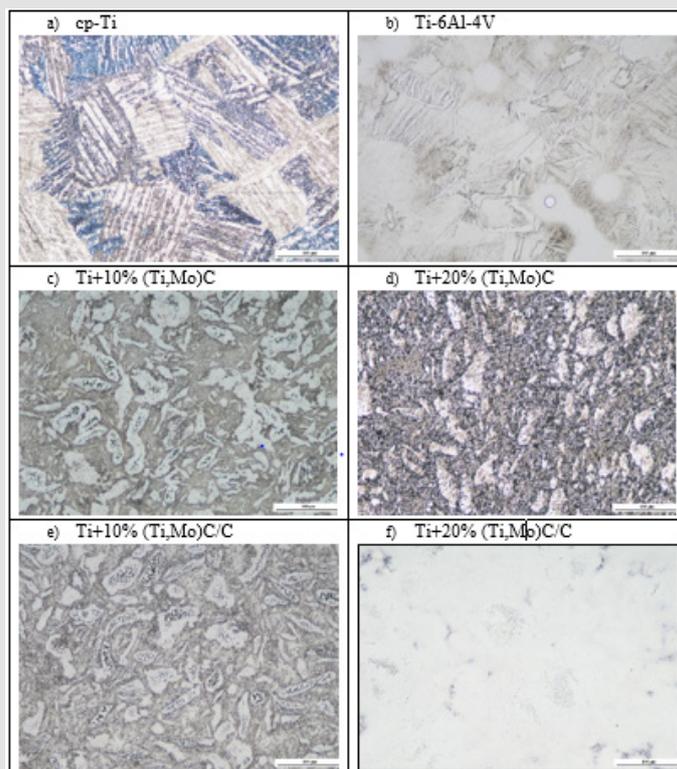


Figure 2: The microstructure of sintered materials. The scale shown in the images is 100 microns.

For selected materials tested corrosion. Polarizing curves for titanium and titanium composites are shown in (Figure 3). Corrosion tests were carried out in Ringer's solution, an electrolyte with a composition similar to extracellular fluid, simulating body fluids. Corrosion parameters of sintered materials are shown in (Table 2) In case of pure Ti sample immersed in artificial saliva solution, corrosion potential was at the level of -0.328 V and corrosion current density reached $2.1 \cdot 10^{-6}\text{ A}\cdot\text{cm}^{-2}$, and in the case of Ti-6Al-4V alloy corrosion potential was at the level of -0.392 V and corrosion current density reached $2.3 \cdot 10^{-6}\text{ A}\cdot\text{cm}^{-2}$ Corrosion results shows that the composites generally displayed similar polarization curves

and passivity characteristics. However, the corrosion potentials (E_{corr}) of the composites were clearly distinct and occurred in the ranges of -0.498 to -0.643 V . Analysis of the results of corrosion tests showed that the corrosion potential (E_{corr}) and the density of corrosive current (I_{corr}) of composites show a constant tendency to change the value with the increase of the mass fraction of the reinforcement phase. When titanium composites were immersed in Ringer's solution, the corrosion potential generally shifts to lower values towards cathodic region. Also, corrosion current increased with increasing reinforcing phase content.

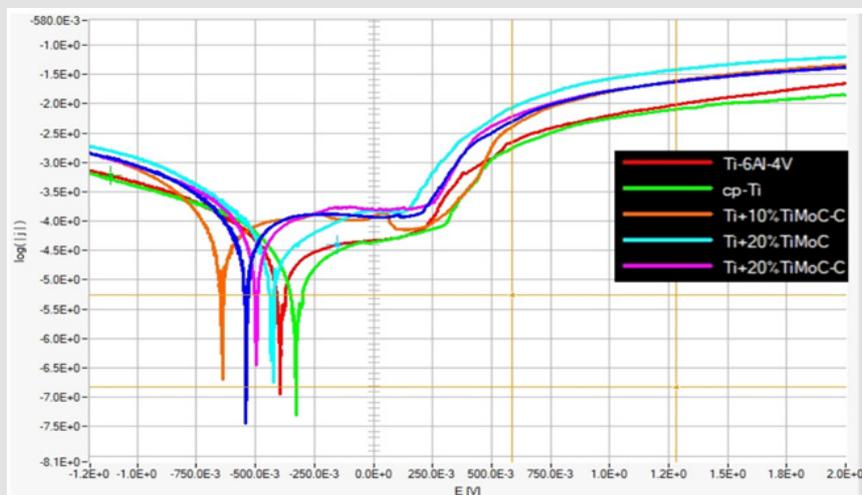


Figure 3: Polarization curves of titanium and titanium-based materials in Ringer's solution.

Summary

Powder contaminations are an obstacle to mass transport processes during the sintering. U-FAST technology allows better control over diffusion processes. Spark discharges generated during sintering remove adsorbed gases and oxides from the surface of particles, facilitating the formation of active contacts between sintered powder particles. This affects the lower sintering temperature and a shorter heating time. This work has already produced perfectly concentrated (100% of theoretical density) titanium material, a popular alloy as well as titanium composite materials at 1050°C by 2min. Together with the applied load, it results in rearrangement of powder particles and obtaining a homogeneous sintered microstructure. The use of 20 wt.% (Ti,Mo)C additive in U-FAST sintering technology allowed to obtain materials with the HV hardness 1203 ± 108 , even up to 600% compared to pure titanium. In the case of 20wt.% of the (Ti,Mo)C/C additive, the material has a hardness of 1581 ± 138 HV, which is over 800% higher than hardness of the pure titanium. Corrosion properties of titanium composites similar to reference cp-Ti and Ti-6Al-4V were obtained. The article shows that U-FAST technology is useful for the production of titanium-based biomaterials. Further optimization of the

powders preparation and sintering processes will contribute to the manufacturing materials with even more favorable parameters.

References

- Poletti C, Balog M, Schubert T, Liedtke V, Edtmaier C (2008) Laser Additive Manufacturing of High-Performance Materials. *Compos Sci Technol* 68(9): 2171-2177.
- Alman DE, Hawk JA (1999) The abrasive wear of sintered titanium matrix-ceramic particle reinforced composites. *Wear* 1: 629-639.
- Gülsoy HO, Gunay V, Baykara T (2015) Influence of TiC, TiN and TiC(N) additions on sintering and mechanical properties of injection moulded titanium based metal matrix composites. *Powder Metall* 58(1): 30-35.
- Da Silva AM, Meyer A, Dos Santos JF, Kwietniewski CEF, Strohaecker TR (2004) *Compos Sci Technol* 64: 1495-1501.
- Gu D, Hagedorn YC, Meiners W, Wissenbach K, Poprawe R (2011) Selective Laser Melting Additive Manufacturing of TiC/AlSi10Mg Bulk-form Nanocomposites with Tailored Microstructures and Properties. *Compos Sci Technol* 71: 1612-1620.
- Figiel P, Garbiec D, Biedunkiewicz A, Biedunkiewicz W, Kochmański P, et al. (2018) Microstructural, Corrosion And Abrasive Characteristics Of Titanium Matrix Composites. *Arch Metall Mater* 63 (4): 2051-2059.
- Wang Z, Zhang H, Guo C, Liu W, Yang Z (2016) *Mater Sci* 51(10): 4996-5007.
- Jach K, Rosiński M (2018) *Ceramic Materials* 70: 293-300.
- Genicore. Ppc sintering machines.

ISSN: 2574-1241

DOI: 10.26717/BJSTR.2019.23.003906

Katarzyna Jach. Biomed J Sci & Tech Res



This work is licensed under Creative Commons Attribution 4.0 License

Submission Link: <https://biomedres.us/submit-manuscript.php>



Assets of Publishing with us

- Global archiving of articles
- Immediate, unrestricted online access
- Rigorous Peer Review Process
- Authors Retain Copyrights
- Unique DOI for all articles

<https://biomedres.us/>